


## U-Epoxy-It

### One Day Metallic Coating System

1. **PREP:** One of the key components is to ensure that the surface is free from sealers, dirt, oils, glues and other contaminants. It also needs profiled.
  - a. A few methods for properly preparing the concrete are:
    - i. Using a lower grit (16, 30) metal bond diamond tool on a single headed or planetary grinder with a vacuum and grinding dry.  
*Note: In order to complete the floor in 'one day' dry grinding is necessary.*
    - ii. Use our Concrete DNA Satellite pad (30 grit)
      1. Also use our Super Blue liquid floor prep
        - Note: When using water to prep allow the floor to dry a minimum of 24 hours before applying coating.
2. **Apply S&P 40 Sealer/Primer Pigmented:** Mix the pigment in the "A" Side for 1-2 minutes. (32 oz per 2 gallon kit) After mixing the pigment with the "A" Side mix with part B. Mix S&P by drill mixing. Apply the product to the floor by dipping and rolling out of a pan. Use a 1/4" to 3/8" nap roller cover. Larger floors can be accomplished by pouring the S&P 40 on the floor and using a pad applicator to spread the product. Coverage rates for dipping and rolling are approximately 300 sq ft per gallon to 500 sqft per gallon depending on the porosity and surface prep method. S&P is able to be coated over when the surface is tack free and able to be walked on without forming an impression.(typically 4-6 hours). If exceeding maximum recoat window of 12 hours S&P 40 must be screened with 220 or coarser screen on a buffer to ensure adequate epoxy adhesion.
3. **Apply Epoxy Flow 100 with metallic pigment:** Mix the pigment in the "A" Side of the Epoxy Flow 100 for 1-2 minutes using a drill mixer at low speed. After mixing the pigment with the "A" Side mix with part B. Epoxy Flow 100 is to be mixed as 2 parts "A" to 1 part "B" Mix Flow 100 Gloss by drill mixing. After mixing immediately pour the product on the floor. (do not let the product dwell in a bucket). Spread by using a notched squeegee and back roll with a roller. Application rates are typically 60 to 100 sq ft per gallon. For metallics many creative aspects can be achieved by using erratic rolling patterns, using other metallic colors in areas as highlights, and misting solvents such as xylene on the floor. Testing these techniques is recommended before doing the floor. Spike shoes are a must to walk through the product.
  - a. Our EZ Glo Floor finish can be applied after the epoxy has cured for 24 hours. This adds a sacrificial wear layer to the floor to help with scuffs and scratches. (optional)

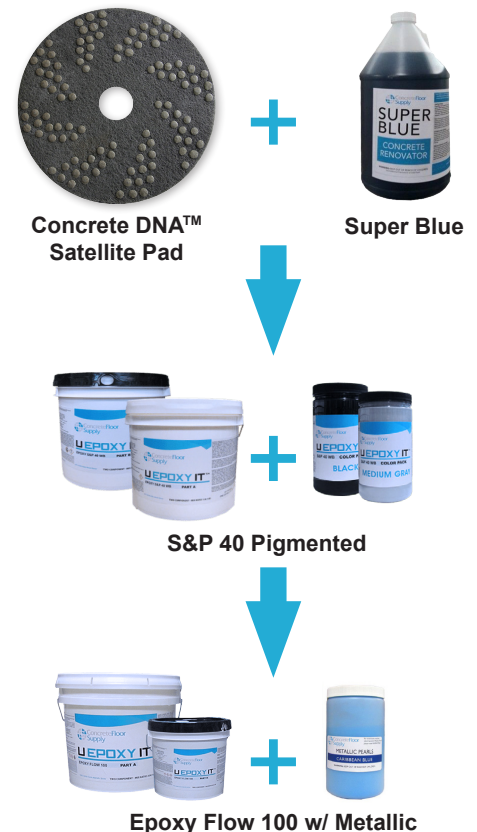

The information supplied by Concrete Floor Supply about our products and uses is not a representation or a warranty. It is supplied on the condition that you will make your own tests to determine the suitability of the product for your own particular purpose. Any use or application is the sole responsibility of the user. Listed physical properties are typical and should not be construed as specifications.